Journal of Materials Science and Emerging Technologies

SCIVOLVE

Research Article

Open Access Full Text Article

The Effect of Accelerated Post-Curing on Haze and Switching Voltages of a UV-Cured PDLC Film Formulation

H. Hakemi[1*]

[1]*Plastic Liquid Crystal Technology, Via Lambro 80, 20846 Macherio (MB), Italy.*

***Correspondence:**

H. Hakemi
Plastic Liquid Crystal Technology, Via Lambro 80, 20846 Macherio (MB), Italy.

Received: March 13, 2026; **Published:** April 02, 2026.

How to cite this article:

H. Hakemi, "The effect of accelerated post-curing on haze and switching voltages of a UV-cured PDLC film formulation," *Journal of Materials Science and Emerging Technologies*, vol. 1, no. 2, pp. 1–5, 2026.

Abstract

The influence of accelerated ultraviolet (UV) post-curing on the electro-optical (EO) performance of an industrial polymer-dispersed liquid crystal (PDLC) formulation was systematically investigated under production-relevant conditions. Primary curing intensity was varied within 40–200 mW/cm² range to establish baseline relationships between curing kinetics, morphology, haze (Hon), and switching voltages (V_{10} and V_{90}). Subsequently, accelerated post-curing treatments were applied on samples cured at 43.2, 106.5, and 162.8 mW/cm². Increasing primary curing intensity resulted in a near-linear decrease in haze and switching voltages, indicating improved polymer network homogeneity and refractive index matching. In contrast, accelerated post-curing consistently increased normal haze and produced minor but systematic variations in switching voltages.

Keywords: Polymer-dispersed liquid crystal (PDLC), UV curing, accelerated post-curing, haze, switching voltage, morphology, phase separation.

1. Introduction

Polymer Dispersed Liquid Crystals (PDLCs) have been extensively studied for smart glazing and optical modulation applications. The electro-optical performance of PDLC depends strongly on polymerization-induced phase separation (PIPS), which governs droplet size distribution, interfacial anchoring strength, and refractive index matching. The curing intensity, temperature, exposure time, and formulation composition collectively determine polymer network architecture and resulting electro-optical behavior.

The effect of material and process parameters on electro-optical properties of industrial-scale PDLC films are essential for manufacturing of high-quality products. Among the material parameters, such as chemical and physical properties and composition, as well as process parameters, such as curing intensity, temperature and time; thickness; natural aging; phase separation and curing kinetics are important factors influencing the electro-optical properties of PDLC films [1-17]. In particular, the effect of material composition on morphology and electro-optical properties in various PDLC film formulations have been also reported in some recent literature [18-26]. More specifically, the process parameter such as curing UV intensity have also shown to be dominant contributing factors on the kinetics of phase separation and polymerization, morphology and electro-optical properties of PDLC films [27-32].

Other recent studies and review showed that higher cure temperature or longer cure times tend to increase polymer crosslinking and can change droplet size/distribution, transmissions and switching voltages. Multiple experimental datasets confirm higher UV dose and longer exposure tends to accelerate phase separation, yielding to various droplet morphologies with predictable effects on electro-optical performances of PDLC [13-15, 33-36].

Although primary UV curing conditions have been widely investigated, the influence of accelerated post-curing on already-formed PDLC morphology remains less reported in the literature. Secondary UV exposure may induce additional crosslinking, polymer shrinkage, interfacial stress redistribution and droplet morphology evolution, where understanding these mechanisms is critical for production-line optimization.

The present work is the continuation of our previous studies [10-15, 24-26] regarding the effect of material and process parameters on the morphology, optical transmissions, switching voltage and response times of industrial-scale flexible PDLC films for product manufacturing. Consequently, in continuation of those reports, here we focused on the effect of accelerated UV post-curing on the normal haze and switching voltages of a PDLC formulation to understand if it would be appropriate for industrial scale up

and production. The detailed results of this work are described in the following sections.

2. Materials and Methods

The utilized PDLC materials consisted of commercial QYPDLC142 (QY142) liquid crystal mixture (Qingdao), NOA65 (N65) pre-polymer resin (Norland Optical Adhesive), acrylic acid (AA) index-matching additive (Kaitai), Tinuvin TV-400 (TN400) UV absorber (BASF) Irga-cure 819 (Irg819) and 184 (Irg814) photo-initiators (Ciba), 25µm Nano (NM) Micro micro-spacers (Suzhou) and 175 µm ITO-PET transparent conductive films (Eastman). The material compositions (weight%) of PDLC formulation were:

Q142/N65/AA/TV400/Irg819/Irga184/ micro-spacer25um (40%/51%/4%/4%/0.5%/1%/0.6%).

The uncured PDLC mixture was pre-heated at 45°C for 10 minutes and then was poured between the vertical gap of two ITO-PET rolls on a custom-made coater/laminator system (Sigma Sivo). Under the coating rolls, the uncured coated films were passed through a pressure roll to insure the uniformity of the PDLC film thickness. The uncured PDLC film was then cured through a custom-made UV-IR conveyor system at UV intensity of 165 mW/cm^2 and 0.15 meter/minute line speed. The thickness homogeneity of PDLC layers were further insured by micro-spacers. Further details on effects of other process parameters, such as UV intensity, cure temperature, cure time, film thickness and liquid crystal concentration on morphology and electro-optical properties of PDLC films have been mentioned elsewhere [10-15, 24-26].

The electro-optical properties of the PDLC film was measured on the as-made samples. The threshold voltage (V_{10}) and saturation voltage (V_{90}) were measured from transmission-voltage curves on a specially constructed photometric system consisting of a white light source, sample chamber, a photometer, an amplifier, a function generator and electronic data acquisition network with VAC square wave at 100 Hz frequency. The on-state haze (H_{on}) of PDLC films was measured by BYK-Gardner model XL835 haze-meter. Further details of these experimental setups and measurements have been mentioned elsewhere [10-15, 24-26].

3. Results and Discussion

In order to provide a comparative background, the haze and switching voltages of PDLC film were first measured as a function of UV curing within 40-200 mW/cm^2 range. The results of the effect of UV curing intensity (IUV) on H_{on}, V_{10} and V_{90} are presented in Figure-1. The results clearly indicate that, by increasing the UV intensity, both haze and switching voltages decrease almost linearly. Increasing primary UV intensity reduced both haze and switching voltages. Faster polymerization likely produces finer droplet distributions and improved refractive index matching, thereby lowering scattering and electric-field requirements. Such correlation between haze and switching voltages indicates that lowering of V_{10} and V_{90} by increasing the UV intensity are due to favorable morphology, LC droplet alignments and anchoring energy that resulted to reduction of switching voltage consumptions.

Subsequently, the electro-optical properties of utilized PDLC

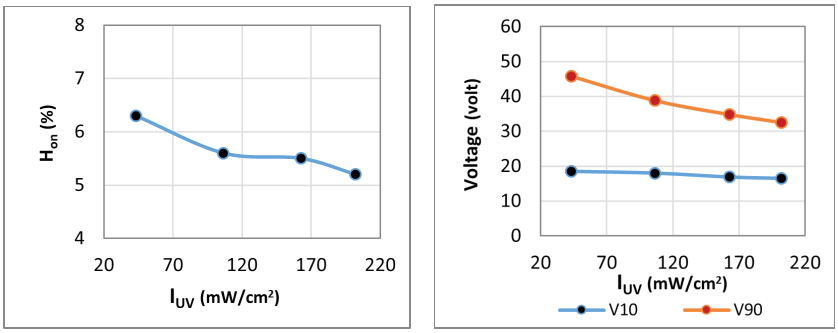

Figure-1: The haze and switching voltages of PDLC film as a function of UV curing intensity

film formulation were studied under various UV post-curing intensities. Accordingly, we studied the effect of post-curing on haze and switching voltages of PDLC film at three 43.2 mW/cm^2, 106.5 mW/cm^2 and 162.8 mW/cm^2 UV curing intensities. The results are presented in Figures 2-4, where at constant curing energy both haze and switching voltages increase by increasing post-curing intensity. While higher curing energy improves the haze and switching voltages (see Figure 1), post curing energy demonstrates opposite effect. Namely, the accelerated post-curing at all tested intensities increased the Hon, whereas the V_{10} and V_{90} exhibited minor but systematic variations depending on initial curing conditions. The trends of haze and switching voltages by accelerated post-curing are in contrast with our previous work on similar PDLC formulation, where both haze and switching voltages decreased upon natural aging process.

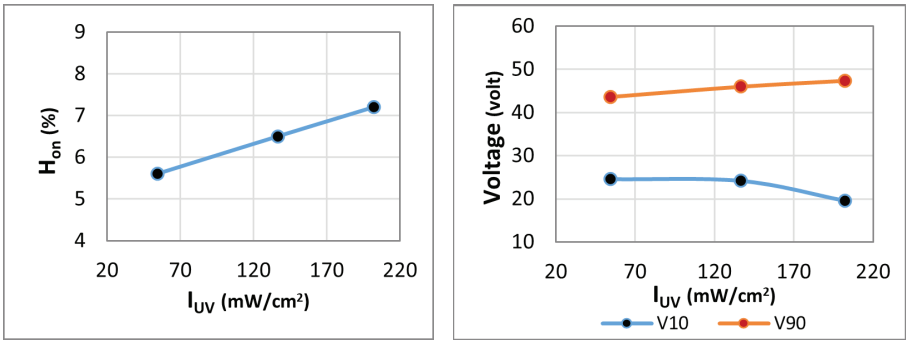

Figure-2: The effect of post-curing on haze and switching voltages of PDLC film cured at 43.2 mW/c

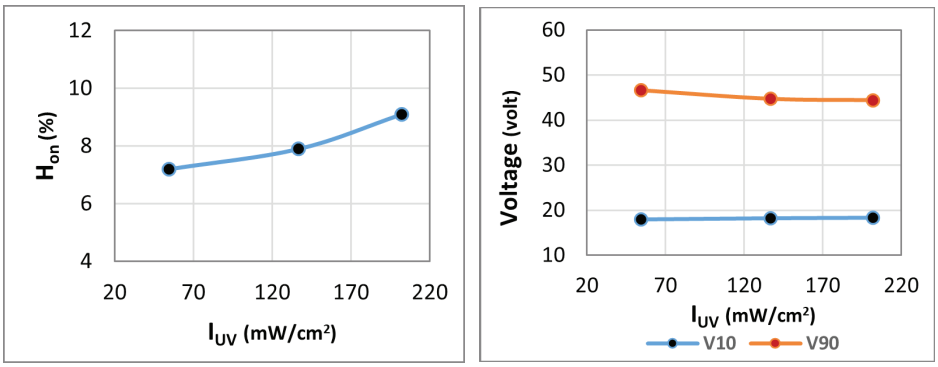

Figure-3: The effect of post-curing on haze and switching voltages of PDLC film cured at 106.5 mW/cm^2

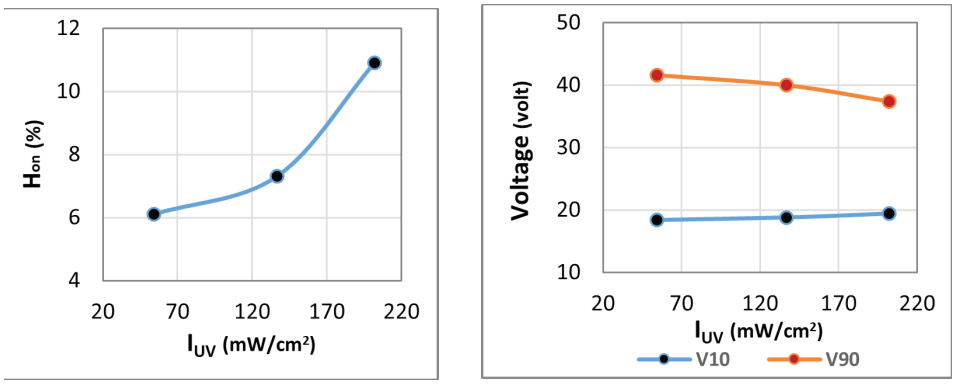

Figure-4: The effect of post-curing on haze and switching voltages of PDLC film cured at 162.8 mW/cm^2

In general, the accelerated post-curing of PDLC provide the phase separation and network formation to continue or relax, therefore the droplet size/shape and polymer stiffness change after the initial cure. That in turn, affects the optical transmissions, switching voltages, contrast ratio and response times.

According to Figures 2-4, the effect of post-curing on PDLC film clearly indicates that Hon increases at all three UV curing intensities. Such increasing trend of Hon by increasing the post-curing intensity seems be due to refractive index miss-matching caused by change in the morphology, in accordance with other studies [37-40] that post-curing decreases the liquid crystal droplet sizes and scattering efficiencies. On the other hand, the effect of accelerated post-curing on the switching voltages provides various trends. Although these trends are not as large as in Hon, but requires some detail explanation. For example, according to Figures 2-4, the threshold voltage V_{10} exhibits a small decreasing trend at 43.2mW/cm^2, but is invariant at 106.5mW/cm^2 and 162.8mW/cm^2 curing intensities. Whereas the saturation voltage V_{90} exhibits a small increasing trend at 43.2mW/cm^2, but shows small decreasing trends at 106.5mW/cm^2 and 162.8mW/cm^2 curing intensities. In general, the switching voltage evolution under accelerated post-curing is governed by a coupled interaction between droplet radius reduction, anchoring enhancement, polymer modulus increases and possible changes in effective elastic constant. The modest experimental voltage shifts observed in this study are consistent with partial compensation among these parameters. In short, upon post-curing, the experimentally observed minor voltage variations indicate near-compensation between morphology, anchoring energy and elastic contributions. In contrast, the haze increase is dominated by refractive index mismatch amplification and droplet size redistribution.

4. Conclusion

In this report at first only pre curing was tested and it was found out that working in very high energies can improve EO/haze properties and can lead to better homogeneity in morphology (V_{90}-V_{10} is lower). Adding post curing to the system has bad effect on morphology and thus also on haze. This should be because of temperature in the UV box, or inhomogeneity in the UV flux/temperature on the way of the film. The accelerated UV post-curing increases haze and provides no significant advantage in switching voltage reduction. A brief conclusion of the accelerated post-curing on utilized PDLC formulation under the tested conditions are as follows:

- Increasing primary UV curing intensity improves electro-optical performance by reducing haze and switching voltages.
- Accelerated UV post-curing increases haze at all tested intensities, indicating morphology changes and refractive index mismatch. Switching voltages exhibit only minor variations under post-curing, suggesting partial compensation between droplet modification and anchoring energy effects.
- Post-curing under the tested industrial conditions is not beneficial for this PDLC formulation.

The findings of this study demonstrate that, accelerated UV post-curing of utilized PDLC formulation is not beneficial for large-scale industrial production and may induce morphological over-stabilization that degrades optical homogeneity. Further recommended studies could include, utilizing accelerated post-curing on other PDLC formulations, comparative natural aging, morphological characterization via SEM and light scattering, FTIR residual conversion analysis and controlled thermal annealing experiments.

Acknowledgement

This study had been funded by Gauzy Ltd -Israel and carried

out at company's R&D laboratories as part of PDLC industrial development program during 2015-2016 period.

References

[1] C. E. Hoppe, M. J. Galante, P. A. Oyanguren, and R. J. J. Williams, "Polymer-Dispersed Liquid Crystals with Co-continuous Structures Generated by Polymerization-Induced Phase Separation of EBBA–Epoxy Solutions," *Macromolecules*, vol. 35, no. 16, pp. 6324–6331, 2002. doi:10.1021/ma0200120.

[2] M. Mucha, "Polymer as an important component of blends and composites with liquid crystals," *Progress in Polymer Science*, vol. 28, no. 5, pp. 837–873, 2003. https://doi.org/10.1016/S0079-6700(02)00117-X.

[3] C. E. Hoppe, M. J. Galante, P. A. Oyanguren, and R. J. J. Williams, "Optical properties of novel thermally switched PDLC films composed of a liquid crystal distributed in a thermoplastic/thermoset polymer blend," *Materials Science and Engineering: C*, vol. 24, no. 5, pp. 591–594, Nov. 2004. https://doi.org/10.1016/j.msec.2004.08.002.

[4] S. Bronnikov, S. Kostromin, and V. Zuev, "Polymer-dispersed liquid crystals: Progress in preparation, investigation, and application," *Journal of Macromolecular Science, Part B*, vol. 52, no. 12, pp. 1718–1735, 2013. https://doi.org/10.1080/00222348.2013.808926.

[5] C. Zhang, D. Wang, H. Cao, P. Song, C. Yang, H. Yang, and G.-H. Hu, "Preparation and electro-optical properties of polymer dispersed liquid crystal films with relatively low liquid crystal content," *Polymer Advanced Technologies*, vol. 24, pp. 453–459, 2013. https://doi.org/10.1002/pat.3103.

[6] R. Yamaguchi and S. Sakurai, "Cell thickness dependence on electric optical property of reverse mode liquid crystal display," *Journal of Photopolymer Science and Technology*, vol. 27, no. 3, pp. 287–290, 2014.

[7] Y. J. An, X. L. Geng, S. H. Zhang, and Z. Q. Du, "Preparation and performance testing of flexible PDLC films," *Advanced Materials Research*, vol. 1015, pp. 89–92, 2014.

[8] J. Kim and J. I. Han, "Effect of liquid crystal concentration on electro-optical properties of polymer dispersed liquid crystal lens for smart electronic glasses with auto-shading and auto-focusing function," *Electronic Materials Letters*, vol. 10, no. 3, pp. 607–610, 2014.

[9] M. Ellahi and M. Y. Rafique, "Electro-optical properties of PDLC films using diethylenetriamine (DETA) hardener," *Molecular Crystals and Liquid Crystals*, vol. 638, no. 1, pp. 103–110, 2016. https://doi.org/10.1080/15421406.2016.1222037.

[10] H. Hakemi, "Effect of thickness on morphology and electro-optics of a plastic thermoset polymer dispersed liquid crystal," *Molecular Crystals and Liquid Crystals*, vol. 681, no. 1, pp. 12–22, 2019.

[11] H. Hakemi, "The effect of thickness on electro-optical properties of a UV-curable polymer dispersed liquid crystal," *Molecular Crystals and Liquid Crystals*, vol. 689, no. 1, pp. 34–43, 2019.

[12] H. Hakemi, "The effect of cure temperature and time on the morphology and electro-optical properties of flexible thermoset PDLC films," *Molecular Crystals and Liquid Crystals*, vol. 703, no. 1, pp. 1–12, 2020.

[13] H. Hakemi, "The effect of cure temperature on the morphology and electro-optical properties of flexible UV-cured PDLC films," *Recent Progress in Materials*, vol. 2, no. 4, p. 11, 2020.

[14] H. Hakemi, M. Khenkin, R. Tamari, and D. Gal-Fuss, "Transient phenomenon in polymer-dispersed liquid crystals," *Recent Progress in Materials*, vol. 2, no. 1, pp. 1–11, 2020. https://doi.org/10.21926/rpm.2001006.

[15] H. Hakemi, "The effect of liquid crystal concentration on electro-optical properties of five flexible polymer dispersed liquid crystal formulations," *Material Science and Engineering International Journal*, vol. 7, no. 4, pp. 217–221, 2023. https://doi.org/10.15406/mseij.2023.07.00226.

[16] W. Ahn and K. Ha, "Temperature effects on LC droplets formation of PDLC films with thermoplastic matrix," *Korea Polymer Journal*, vol. 7, no. 2, pp. 130–135, 1999..

[17] G. Chen, W. Hu, L. Zhou, H. Zhang, L. Wang, C. Zhang, J. Sun, L. Zhang, X. Yuan, and S. Zhu, "Growth and characterization of high-quality GaN crystals by the sodium flux method," *Crystals*, vol. 11, art. no. 576, 2021.

[18] S. J. Kłosowicz and M. Aleksander, "Polymer-dispersed liquid crystals prepared by different methods," *Opto-Electronics Review*, vol. 12, no. 3, pp. 305–312, 2004..

[19] S. A. Bulgakova, A. I. Mashin, I. A. Kazantseva, D. E. Kashtanov, M. M. Jones, G. S. Tsepkov, A. V. Korobkov, and A. V. Nezhdanov, "Influence of the composition of the polymer matrix on the electrooptical properties of films with a dispersed liquid crystal," *Russian Journal of Applied Chemistry*, vol. 81, no. 8, pp. 1446–1451, 2008. https://doi.org/10.1134/S1070427208080292.

[20] L. Lu, S.-Y. Lu, and L.-C. Chien, "Fast-switching electro-optical films based on polymer encapsulated liquid crystal, carbon nanotube, and dye," in Proc. SPIE 7232, *Emerging Liquid Crystal Technologies IV*, 2009, art. no. 723204. https://doi.org/10.1117/12.812336.

[21] J. Kim and J. I. Han, "Effect of liquid crystal concentration on electro-optical properties of polymer dispersed liquid crystal lens for smart electronic glasses with auto-shading and auto-focusing function," *Electronic Materials Letters*, vol. 10, no. 3, pp. 607–610, 2014. https://doi.org/10.1007/s13391-014-3264-2.

[22] D. Jayoti and P. Malik, "Electro-optical properties of polymer dispersed liquid crystal films prepared by different techniques," *Soft Matter*, vol. 357, no. 1, pp. 148–154, 2015.

[23] G. Chen, L. Zhou, L. Wang, and S. Zhu, "Growth and characterization of high-quality GaN crystals by the sodium flux method," *Crystals*, vol. 11, no. 6, art. no. 576, 2021. https://doi.org/10.3390/cryst11060576.

[24] H. Hakemi, "Effect of nanoparticles on the mechanical properties of polymer composites," *Materials Science and Engineering International Journal*, vol. 5, no. 5, pp. 153–158, 2021. https://doi.org/10.15406/mseij.2021.05.00153.

[25] H. Hakemi, "The effect of process parameters on morphology and electro-optics of a polymer dispersed liquid crystal formulation," *Journal of Modern Research in Engineering and Technology*, vol. 7, no. 2, pp. 1–12, 2022.

[26] H. Hakemi, "Preparation and characterization of polymer dispersed liquid crystal films using UV curing method," *Journal of Modern Research in Engineering and Technology*, vol. 7, no. 2, pp. 26–29, 2022.

[27] E. Nastał, E. Żurańska, and M. Mucha, "Polymer–liquid crystal composites: Morphology and properties," *Journal of Polymer Science Part B: Polymer Physics*, vol. 37, no. 4, pp. 455–463, 1999. https://doi.org/10.1002/(SICI)1099-0488(19990215)37:4.

[28] O. Yaroshchuk, F. Elouali, and U. Maschke, "Polymer–liquid crystal composites: Preparation methods and electro-optical properties," *Optical Materials*, vol. 32, no. 9, pp. 982–989, 2010. https://doi.org/10.1016/j.optmat.2010.03.004.

[29] F. Z. Elouali, O. Yaroshchuk, and U. Maschke, "Polymer–liquid crystal composites: Preparation methods and electro-optical properties," *Molecular Crystals and Liquid Crystals*, vol. 526, pp. 1–9, 2010. https://doi.org/10.1080/15421401003763984.

[30] F. Ahmad, M. Jamil, J. W. Lee, S. R. Kim, and Y. J. Jeon, "The effect of UV intensities and curing time on polymer dispersed liquid crystal (PDLC) display: A detailed analysis study," *Electronic Materials Letters*, vol. 12, no. 4, pp. 685–692, 2016. https://doi.org/10.1007/s13391-016-6012-7.

[31] F. Z. Abdoune, L. Benkhaled, X. Coqueret, U. Maschke, and L. Mechernene, "Effects of ultraviolet-curing conditions on the electro-optical behavior of polymer dispersed liquid crystal films," *Liquid Crystals*, vol. 37, no. 2, pp. 163–172, 2010. https://doi.org/10.1080/02678290903428507.

[32] F. Z. Abdoune, L. Benkhaled, L. Méchernène, and U. Maschke, "Effect of curing process on the dynamic response of polymer dispersed liquid crystal films," *Macromolecular Symposia*, vol. 301, no. 1, pp. 101–106, 2011. https://doi.org/10.1002/masy.201150214.

[33] J. Xu, H. Li, L. Guo, Z. Zhang, C. Zou, Q. Wang, H. Yang, X. Wang, M. Yu, and Y. Gao, "Preparation and electro-optical properties of polymer dispersed liquid crystal films by UV curing," *Crystals*, vol. 12, no. 11, art. no. 1551, 2022. https://doi.org/10.3390/cryst12111551.

[34] A. Mouquinho and J. Sotomayor, "The impact of curing temperature and UV light intensity on the performance of polymer-dispersed liquid crystal devices exhibiting a permanent memory effect," *Crystals*, vol. 14, no. 6, art. no. 571, 2024. https://doi.org/10.3390/cryst14060571.

[35] S. Agarwal, S. Srivastava, S. Joshi, S. Tripathi, B. P. Singh, K. K. Pandey, and R. Manohar, "Electro-optical behavior of polymer dispersed liquid crystal films under varying curing conditions," *ACS Materials Au*, vol. 5, no. 1, pp. 188–214, 2025. https://doi.org/10.1021/acsmaterialsau.5c00012.

[36] D. E. Lucchetta, L. Lucchetti, L. Gobbi, and F. Simoni, "Electro-optical properties of polymer dispersed liquid crystal films prepared by UV-induced phase separation," *Molecular Crystals and Liquid Crystals*, vol. 360, no. 1, pp. 93–103, 2006. https://doi.org/10.1080/15421400600605259.

[37] Z. Huang, G. Chidichimo, G. De Filpo, A. Golemme, H. Hakemi, and M. Santangelo, "Phase separation in polymer dispersed liquid crystals with two different reacting monomers," *Liquid Crystals*, vol. 23, no. 4, pp. 519–524, 1997. https://doi.org/10.1080/026782997208109.

[38] R. Caputo, L. De Sio, A. Veltri, C. Umeton, and A. V. Sukhov, "Electrically controlled diffraction gratings in polymer-dispersed liquid crystals," *Optics Letters*, vol. 29, no. 11, pp. 1261–1263, 2004. https://doi.org/10.1364/OL.29.001261.

[39] V. K. S. Hsiao, T. J. White, A. N. Cartwright, P. N. Prasad, and C. A. Guymon, "Photopolymerization of liquid crystal/monomer mixtures: Effect of monomer functionality on phase separation and electro-optical properties," *European Polymer Journal*, vol. 46, no. 5, pp. 937–943, 2010. https://doi.org/10.1016/j.eurpolymj.2010.02.004

[40] M. Bouchakour, Y. Derouiche, Z. Bouberka, C. Beyens, and F. Riahi, "Electro-optical properties of polymer dispersed liquid crystal films prepared by UV curing," *Liquid Crystals*, vol. 42, no. 11, pp. 1527–1536, 2015. https://doi.org/10.1080/02678292.2015.1039960.

Copyright: ©2026 H. Hakemi. This is an open-access article distributed under the terms of the Creative Commons Attribution License, which permits unrestricted use, distribution, and reproduction in any medium, provided the original author and source are credited. To view a copy of this licence, visit https://creativecommons.org/licenses/by/4.0/